

University of Texas Rio Grande Valley

ScholarWorks @ UTRGV

Chemistry Faculty Publications and
Presentations

College of Sciences

10-28-2022

Recent advances in computational study and design of MOF catalysts for CO₂ conversion

Haoyuan Chen

The University of Texas Rio Grande Valley

Follow this and additional works at: https://scholarworks.utrgv.edu/chem_fac

 Part of the [Chemistry Commons](#)

Recommended Citation

Chen H (2022) Recent advances in computational study and design of MOF catalysts for CO₂ conversion. Front. Energy Res. 10:1016406. doi: 10.3389/fenrg.2022.1016406

This Article is brought to you for free and open access by the College of Sciences at ScholarWorks @ UTRGV. It has been accepted for inclusion in Chemistry Faculty Publications and Presentations by an authorized administrator of ScholarWorks @ UTRGV. For more information, please contact justin.white@utrgv.edu, william.flores01@utrgv.edu.



OPEN ACCESS

EDITED BY

Kui Tan,
The University of Texas at Dallas,
United States

REVIEWED BY

Nicolaas Vermeulen,
NuMat Technologies, United States

*CORRESPONDENCE

Haoyuan Chen,
haoyuan.chen@utrgv.edu

SPECIALTY SECTION

This article was submitted to Carbon
Capture, Utilization and Storage,
a section of the journal
Frontiers in Energy Research

RECEIVED 10 August 2022

ACCEPTED 14 October 2022

PUBLISHED 28 October 2022

CITATION

Chen H (2022), Recent advances in
computational study and design of MOF
catalysts for CO₂ conversion.
Front. Energy Res. 10:1016406.
doi: 10.3389/fenrg.2022.1016406

COPYRIGHT

© 2022 Chen. This is an open-access
article distributed under the terms of the
[Creative Commons Attribution License](#)
(CC BY). The use, distribution or
reproduction in other forums is
permitted, provided the original
author(s) and the copyright owner(s) are
credited and that the original
publication in this journal is cited, in
accordance with accepted academic
practice. No use, distribution or
reproduction is permitted which does
not comply with these terms.

Recent advances in computational study and design of MOF catalysts for CO₂ conversion

Haoyuan Chen*

Department of Chemistry, The University of Texas Rio Grande Valley, Edinburg, TX, United States

Catalytic conversion of the greenhouse gas CO₂ into value-added chemicals and fuels is highly beneficial to the environment, the economy, and the global energy supply. Metal-organic frameworks (MOFs) are promising catalysts for this purpose due to their uniquely high structural and chemical tunability. In the catalyst discovery process, computational chemistry has emerged as an essential tool as it can not only aid in the interpretation of experimental observations but also provide atomistic-level insights into the catalytic mechanism. This Mini Review summarizes recent computational studies on MOF-catalyzed CO₂ conversion through different types of reactions, discusses about the usage of various computational methods in those works, and provides a brief perspective of future works in this field.

KEYWORDS

computational chemistry, metal-organic framework (MOF), CO₂ conversion, density functional theory (DFT), computational catalysis

Introduction

Reducing the emissions of greenhouse gases, primarily CO₂, into the atmosphere to address climate change has become an urgent, global environmental issue in recent years. Numerous efforts have been made to develop efficient technologies for physically capturing CO₂ from the air *via* adsorption into solid-state materials or absorption into liquids (Yu et al., 2012). Going one step further, CO₂ can also be chemically converted into value-added chemicals and fuels, which not only reduces CO₂ emissions but also produces a useful feedstock for the chemical industry and boosts the global energy supply (Huang and Tan, 2014). However, CO₂ is highly stable and fairly inert, which makes such conversions energy intensive. If the energy cost would result in a net positive flow of CO₂, then the process is not accomplishing the task of reducing CO₂ emission. Developing efficient catalysts for CO₂ conversion under mild conditions is therefore necessary for making those reactions practically useful.

Recently, a large number of metal-organic framework (MOF) materials have been designed as CO₂ conversion catalysts and have shown promising performances (Beyzavi et al., 2015; Li et al., 2018; Li et al., 2020; Zhao et al., 2021a). MOFs are crystalline, nanoporous materials formed by the assembly of inorganic nodes and organic linkers in a

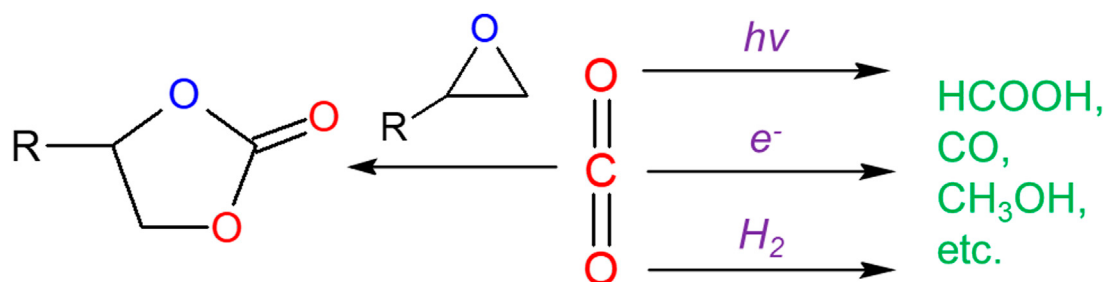


FIGURE 1
Main routes of CO₂ conversion into value-added chemicals and fuels.

TABLE 1 Comparison of cluster, periodic and multi-level models in computational catalysis.

Model	Pros	Cons
Cluster	• Small model size • More options on level of theory	• Truncation can be somewhat arbitrary • May omit key guest-pore interactions
Periodic	• Complete representation of system • Can start directly from crystal structure	• Large system (unit cell) size • Limited options on density functional
Multi-level	• Balance accuracy and cost	• Model construction is non-trivial

combinatorial fashion, which enables fine-tuning of their structural and chemical properties *via* atomically precise design. The excellent structural integrity of MOFs also greatly facilitates computational studies, which often require well-defined atomic coordinates as starting points. Due to the rapid development in methods, algorithms and computing power, computational chemistry has become an essential tool in the investigation of a wide variety of chemical problems. Computational studies not only complement experiments by delivering atomistic-level explanation on experimental observations but also possess increasing predictive power in searching for molecules/materials with even better performance in a certain application. Indeed, many synergistic computational-experimental studies on MOFs for catalytic CO₂ conversion have been published in recent years, which will be discussed in the following sections of this Mini Review.

Catalytic conversion of CO₂ into cyclic carbonates

The most studied route of catalytic CO₂ conversion into value-added chemicals is the cycloaddition between CO₂ and epoxides (Figure 1), which produces five-membered cyclic carbonates (CCs). CCs are versatile chemicals which can be utilized as solvents, battery electrolytes and building blocks in the synthesis of plastics and pharmaceuticals. Schaffner et al.

(2010) This reaction also has a remarkable atom economy of 100%. Since the first report of MOF-catalyzed cycloaddition between CO₂ and epoxides in 2009 (Song et al., 2009), a wide variety of MOFs have been tested for this reaction, in which the catalytic mechanism could vary significantly among different MOFs.

Cluster-based density functional theory (DFT) calculations have been routinely employed to carve out the active site cluster from the periodic MOF structure, map out the reaction pathways and calculate the energy barriers to elucidate the catalytic mechanism (Table 1; Figure 2). Beyzavi et al. (2014) discovered that the MOF Hf-NU-1000 can catalyze the epoxide ring-opening step of this reaction by donating protons from the ligated aqua and OH ligands on its Hf-node. For aromatic substrates, the aromatic rings in the linker can further stabilize the transition state (TS) *via* π -stacking. Kathalikkattil et al. (2015) synthesized and studied an eco-friendly Zn-glutamate MOF which catalyzes CO₂-propylene oxide (PO) cycloaddition through synergistic involvement of Lewis acid (Zn), Lewis base (amino groups in glutamate) and ring-opening nucleophile (bromide anion from the co-catalyst tetrabutylammonium bromide (TBAB)). Hu et al. (2018) studied the same reaction catalyzed by the Cr-MIL-101 MOF in the presence of TBAB and certified the importance of the synergistic catalytic effect between Lewis acid (Cr) and nucleophile (TBAB). The co-catalyzed reaction was found to have a much lower barrier (18 kcal/mol) than the Cr-MIL-101-alone catalyzed

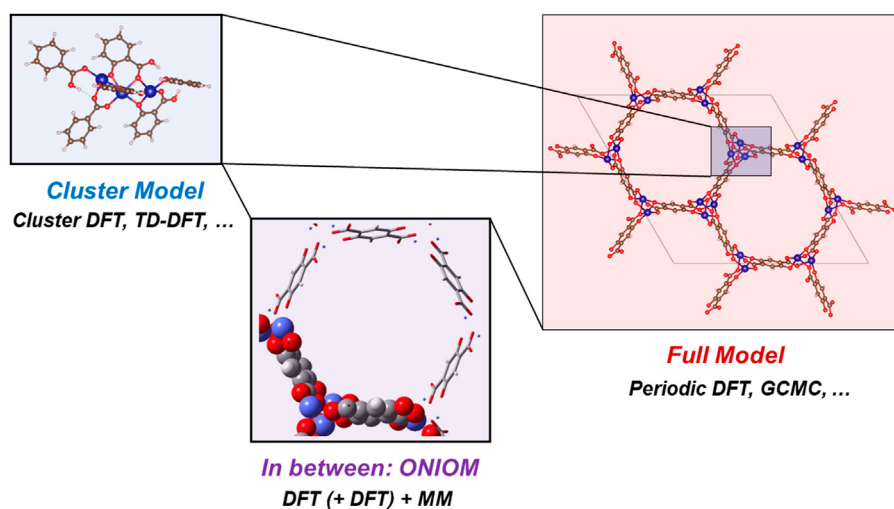


FIGURE 2
Illustration of different levels of models in computational study of MOFs.

(47 kcal/mol) and the TBAB-alone catalyzed (27 kcal/mol) reactions. Similar synergistic effects were observed by [Rachuri et al. \(2019\)](#) and [Wang et al. \(2021\)](#) in a Zn/Cd-adenine MOF and in a Cu₁₂ nanocage-based MOF, respectively. [Parmar et al. \(2019\)](#) showed that iodide can act similarly as bromide in the ring-opening step and mapped out the reaction pathway of CO₂ cycloaddition onto an epoxide-bearing oxindole catalyzed by a Co-MOF and potassium iodide. [Ma et al. \(2022\)](#) designed a Cd-MOF with dynamic metal-iodide bonds that can release iodide anions to facilitate the ring-opening step, which was then confirmed by DFT calculations. [Yang and Jiang. \(2022\)](#) combined DFT calculations and wavefunction analysis to elucidate that the regioselectivity in CO₂-PO cycloaddition co-catalyzed by Cu-MFU-4l/TBAB is a result of the competition between electronic and steric effects.

Without a bromide or iodide cocatalyst, efficient CO₂ conversion to CC has also been achieved with MOF catalysts. [Wu et al. \(2019a\)](#), [Wu et al. \(2019b\)](#) designed a series of MOFs with format linkers and nitrogen-containing ligands which showed good catalytic performance. DFT calculations helped elucidate the role of those ligands in the reaction, which is to activate CO₂ by increasing the nucleophilicity of its oxygen atom for easier nucleophilic attack on epoxide. [Dhankhar et al. \(2021\)](#) also observed in a Cu-MOF with nitrogen-rich linkers that the nitrogen-containing functional groups on the linker can activate CO₂ to facilitate nucleophilic attack, with the help of DFT calculations.

In the aforementioned ten computational works, four density functionals have been used: M06 ([Zhao and Truhlar, 2008](#)), M06-2X ([Zhao and Truhlar, 2008](#)), M06-L ([Zhao and Truhlar, 2006](#)), and B3LYP. [Vosko et al. \(1980\)](#), [Lee et al. \(1988\)](#), [Becke. \(1993\)](#) M06, M06-2X, and B3LYP are among the most widely used

functionals in computational chemistry due to their versatility and robustness, while M06-L has been extensively used for transition metals. Besides cluster-based DFT, periodic DFT has also been employed to investigate this catalytic reaction, which eliminates the procedure of carving out the active site cluster by including the entire periodic structure in the calculation ([Table 1](#); [Figure 2](#)). However, due to the high computational cost associated with large unit cells of MOFs (often hundreds of atoms) and limited options on functionals (using hybrid functionals such as B3LYP often increase the computational cost significantly in periodic systems), the usage of periodic DFT in MOF catalysis is less common (albeit on the rise recently). The only reported mechanistic pathway mapped out by periodic DFT in MOF-catalyzed CO₂-to-CC conversion to date is by [Luo et al. \(2019\)](#), who used the PBE ([Perdew et al., 1996](#)) functional with plane-wave basis sets to study this reaction catalyzed by a Zn-MOF.

To get the benefits of both cluster and periodic DFT, multi-level methods such as ONIOM ([Chung et al., 2015](#)) has been adopted ([Figure 2](#)). In ONIOM, the system is divided into multiple layers, each of which can be described using a different level of theory to balance accuracy and cost ([Table 1](#)). [Xu et al. \(2018a\)](#) constructed a two-layer ONIOM model to study the cycloaddition between CO₂ and styrene oxide catalyzed by Co/Mg-MOF-74, in which an inner layer of 105 atoms around the active site were described using B3LYP while the rest of the system as an outer layer was described by molecular mechanics (MM). [Li et al. \(2019\)](#) adopted a similar strategy to study the cycloaddition between CO₂ and propylene oxide catalyzed by a Cu-MOF NTU-180 and TBAB, in which M06-L was selected for the inner layer. Compared with cluster-based DFT, ONIOM can better capture the noncovalent

interactions that the substrates “feel” in the MOF pores, which may be crucial in certain cases.

Besides mapping out mechanistic pathways, computational methods can help better understand this catalytic reaction in other ways. Zhang et al. (2016), Sharma et al. (2018) and Kong et al. (2021) carried out DFT calculations to locate the most favorable binding sites of CO₂ in different MOFs as starting points of mechanistic investigations. Parmar et al. (2019) performed grand canonical Monte Carlo (GCMC) simulations with MM force fields to obtain the sorption isotherm and binding sites of CO₂ in their Co-MOF, prior to DFT study on cycloaddition reaction pathway. Liao et al. (2020) combined GCMC and DFT to get both the spatial distribution and binding energy of CO₂ in a Cu-MOF named HNUST-9, which exhibited high catalytic activity in CO₂-to-CC conversion. Müller et al. (2019) performed GCMC simulations to screen 12 computationally-generated MOF structures made of the same linker but different inorganic nodes and topologies for CO₂ adsorption. The one with highest CO₂ uptake was then synthesized and exhibited high catalytic activity in CC production.

Photocatalytic reduction of CO₂ into fuels

Another important category of CO₂ conversion reactions is the reduction of CO₂ into fuels such as HCOOH, CO, CH₃OH and CH₄ (Figure 1), also known as “artificial photosynthesis.” This process allows carbon to be reused and can help achieve a carbon neutral economy. Due to the high thermodynamic stability of CO₂, photochemistry is often used to facilitate its reduction. Dhakshinamoorthy et al. (2016) These reactions involve complicated processes such as excitation/emission and electron transfer, which makes computational mechanistic investigations even more useful.

MOFs with photosensitive structural units such as porphyrin/Ru (bpy)₃ (and analogs) in the organic linkers and redox-active metals in the inorganic nodes can be used as photocatalysts. For example, Wang et al. (2019a) performed a thorough computational study on CO₂ photoreduction catalyzed by Co-porphyrin (CoP) and a series of 2D CoP-based MOFs (Co/Zn/Zr-CoPMOF) using periodic DFT calculations. The electronic properties of the MOFs were studied by calculating the partial density of states (PDOS), which confirmed that the 3d states of Co in CoP contribute dominantly to the valence bands (VB) near Fermi level in all those MOFs. Interestingly, the 3d states of Co in Co-oxo clusters in Co-CoPMOF also has significant contribution to the same VB region and formed a low-energy conduction band (CB), which was not observed in Zn/Zr-CoPMOF or CoP itself. This results in a much narrower band gap of Co-CoPMOF (1.2 eV) compared to others (1.6–1.7 eV) and a higher light absorption ratio in Co-CoPMOF (confirmed by absorption spectra calculations),

which could lead to easier electron transfer and higher photocatalytic activity. Indeed, subsequent DFT calculations showed that the CO₂ to CH₄ photoreduction followed the same reaction pathway on all those catalysts and had the same rate-determining step, but Co-CoPMOF had the lowest energy barrier among them. Jin. (2020) conducted a combined experimental-computational study on CO₂-to-formate photoreduction catalyzed by three Zr-MOFs (PCN-222/223/224) with Zn-porphyrin linkers and showed that the catalytic activity may be correlated with the CO₂ binding energy on Zn-porphyrin. Yan et al. (2018) discovered high catalytic activity of CO₂ to formate photoreduction in the Eu-Ru (phen)₃-MOF and showed by DFT that a water molecule coordinated to Eu can be replaced by CO₂ (possibly assisted by light irradiation) to facilitate following reactions. Elcheikh Mahmoud et al. (2019) utilized time-dependent DFT (TD-DFT) to calculate the absorption spectra of a Ru (cptpy)₂-based Zr-MOF AUBM-4 and showed that its photocatalytic activity in CO₂ reduction should come from the Ru-to-cptpy metal-to-ligand charge transfer (MLCT) rather than the Ru-to-Zr metal-to-metal charge transfer (MMCT). Gao et al. (2020) and Stanley et al. (2021) incorporated Ru (bpy)₃ and its analogs into UiO-67 and MIL-101-NH₂, respectively, for photocatalytic CO₂ reduction and conducted DFT calculations to study the reaction mechanism. Sun et al. (2015) doped Ti into the Zr-node in UiO-66-NH₂ and observed enhanced photocatalytic activity in CO₂ reduction. DFT calculations and PDOS analysis revealed that the addition of Ti creates a low-energy CB and facilitates charge transfer. The reduced Ti (Ti³⁺) can further reduce Zr⁴⁺ to Zr³⁺ through MMCT which is catalytically active, therefore acting as a mediator in the charge transfer chain. Wang et al. (2018a), Han et al. (2018), and Wang et al. (2019b) used DFT calculations to show the importance of CO₂-metal binding energy on the photocatalytic activity in Co/Ni-based MOFs and provided strategies to tune this binding energy *via* structural modification.

MOFs have been integrated with other materials to form composite photocatalysts for CO₂ reduction, in which computational methods have also been employed for mechanistic investigation. Xu et al. (2018b) integrated BIF-20, a Zn-MOF with high density of exposed B-H bonds, with graphitic carbon nitride (g-C₃N₄) nanosheets. DFT calculations and electron density analysis demonstrated that upon receiving photoexcited electrons from g-C₃N₄, B-H groups can trap the electron and strengthen CO₂ binding for subsequent reduction reaction. Jiang et al. (2020) grew photosensitive TiO₂ clusters inside the pores of MIL-101 and conducted periodic DFT calculations to find out possible electron transfer pathways. Benseghir et al. (2020) used DFT calculations to obtain the spatial distribution of polyoxometalate (POM) clusters in UiO-67 and elucidated the origin of enhanced photocatalytic activity of this MOF-POM composite. Olowoyo et al. (2020) utilized a semi-empirical tight-binding method to

determine the orbitals in Ti-based MIL-125-NH₂ to understand its photocatalytic activity in CO₂ reduction. Yu et al., (2021) used DFT to elucidate the catalytic mechanism of CO₂ reduction in UiO-66-MoS₂ composite, in which the bridging Mo-O-Zr motif facilitates charge transfer from MoS₂ to Zr⁴⁺ to generate catalytically active Zr³⁺.

Catalytic electro reduction of CO₂ into fuels

Electro catalysis is another solution to facilitate difficult redox reactions such as CO₂ reduction (Figure 1). MOFs, despite having the aforementioned advantages as catalysts, have not been extensively used as electro catalysts until recently due to their often poor conductivity. Downes and Marinescu. (2017) With the discovery of more conductive MOFs as well as MOF-based composites, computational methods have been employed to study the mechanism of catalytic electroreduction of CO₂.

Wang et al. (2018b) designed a POM-metalloporphyrin MOF in which the electron-rich low-valent metals (Mo(V)) in POMs and the macrocycle conjugated π -electron system in metalloporphyrin can boost the electrocatalytic activity together. Periodic DFT calculations showed that the energy barrier of CO₂-to-CO reduction in this MOF is much lower than in POM or metalloporphyrin alone, supporting the hypothesis of synergistic involvement of POM and metalloporphyrin in electron mobility. Huang et al. (2020) used DFT calculations to show that coordinated halogen anions on the Cd metal sites in Cd-metalloporphyrin MOFs NNU-17/18 can help activate bound CO₂ molecules for subsequent electroreduction. Zhong et al. (2020) developed 2D Cu-Zn bimetallic MOFs for CO₂-to-CO electroreduction and revealed different roles of Cu and Zn centers in the catalysis using periodic DFT. Zhu et al. (2021) discovered from DFT calculations that a non-traditional C-H...O hydrogen bond played an important role in stabilizing the adsorbed *CHO intermediate during CO₂ electroreduction catalyzed by the MOF Cu-MFU-4l. Majidi et al. (2021) observed high activity towards CO₂ electroreduction at low overpotentials in a conductive 2D Cu-tetrahydroxyquinone MOF and used periodic DFT to map out the free energy profile. Zhao et al. (2021b) and Kang et al. (2020) combined Cu-based MOFs with Cu nanoparticles and Cu-foam electrodes, respectively, for CO₂ electroreduction and conducted DFT calculations to map out the reaction pathways.

Catalytic chemical hydrogenation of CO₂

Despite many challenges, pure chemical (without photo/electro catalysis) reduction of CO₂ in MOFs has still been

made possible, which is mostly achieved by using H₂ as the reductant to form HCOOH (Figure 1). This requires the heterolytic dissociation of H₂ to a proton and a hydride, which can then attack the oxygen and carbon on CO₂, respectively. Frustrated Lewis pairs (FLPs), in which active Lewis acid and Lewis base groups are separated by steric hinderance, can both bind CO₂ (Ashley and O'Hare, 2013) and heterolytically dissociate H₂ (Stephan and Erker, 2010). The porosity and tunability of MOFs make them excellent platforms for incorporating FLPs. Ye and Johnson (Ye and Johnson, 2015a; Ye and Johnson, 2015b; Ye and Johnson, 2016; Ye et al., 2018) have conducted a series of computational work on exploring MOF-based FLPs for CO₂ hydrogenation. They first studied (Ye and Johnson, 2015a) the mechanism of CO₂ hydrogenation catalyzed by boryl-pyrazole-based FLPs incorporated in UiO-66 using periodic DFT, in which they obtained a low energy barrier but also found that H₂ needs to interact with FLP before CO₂. Otherwise, the barrier increases significantly due to the strong CO₂-FLP binding. They then conducted (Ye and Johnson, 2015b) a computational screening by varying the functional groups on FLP and observed a nearly linear correlation between H₂ binding energy and CO₂ hydrogenation barrier—stronger H₂ binding leads to higher CO₂ hydrogenation barrier. A Sabatier analysis was then carried out to determine the FLP with optimal trade-off between those two quantities. They also extended the scope of their work by studying further hydrogenation to CH₃OH (Ye and Johnson, 2016) and exploring other MOFs (Ye et al., 2018). In the latter work (Ye et al., 2018), GCMC simulations were also performed to identify MOFs with high CO₂ adsorption capacity. Yang and Jiang. (2020) created a FLP in UiO-66 by simply removing one bidentate carboxylate linker from the node and putting a hydroxide ligand on one of the two newly-created open Zr sites to balance the charge. DFT calculations confirmed that the other open Zr site and the hydroxide can act as (frustrated) Lewis acid and base, respectively, to catalyze CO₂ hydrogenation. Heshmat. (2020) revisited the reaction investigated by Ye and Johnson (2015a) using periodic DFT-based *ab initio* molecular dynamics (AIMD) simulations with meta dynamics for enhanced sampling. A stepwise pathway was found to be more favorable in AIMD in contrast to the concerted pathway observed from static DFT, suggesting more mechanistic possibilities for these reactions.

Chemical hydrogenation of CO₂ without FLP has also been achieved using other MOF-based catalysts, most with open metal sites. Maihom et al. (2013) conducted DFT calculations to show that Cu-alkoxide-functionalized MOF-5 can largely reduce the barrier in CO₂-to-HCOOH hydrogenation. An et al. (2019) and Zhang et al. (2021) incorporated Cu/Zn on the nodes in Zr-MOFs and observed synergistic catalytic effect between Cu/Zn and Zr in CO₂ hydrogenation. Qi et al. (2021) combined experiments and DFT calculations to show that in metalloporphyrin-based PCN-224, the Zr-node and the Cu-porphyrin catalyzed different

segments of the CO₂-to-ethanol reaction. Krishnan et al. (2022) computationally screened metalloporphyrin-based MOF-525 (similar to PCN-224) with different metal centers for CO₂-to-HCOOH hydrogenation and identified Rh and Ir as best candidates. Yang and Jiang. (2021) computationally explored MOF-supported N-heterocyclic carbene-stabilized metal hydrides for catalytic CO₂ hydrogenation to produce methanol. Gutterod et al. (2020a), Gutterod et al. (2020b), Zhu et al. (2020) and Mori et al. (2020) incorporated Pt/Cu/PdAg nanoparticles in MOFs for CO₂ hydrogenation and conducted synergistic experimental-computational works to study the nanoparticle-MOF interactions and the catalytic mechanism.

Conclusion and perspectives

In conclusion, computational chemistry has emerged as an essential tool in the study and design of MOF-based catalysts for CO₂ conversion, particularly for providing atomistic-level insights and mapping out mechanistic pictures. DFT-based structural optimizations, energy calculations, transition state searches and wavefunction analyses have been routinely employed in the workflow. With the rapid development of new theoretical and computational methods, we believe that more state-of-the-art tools beyond regular DFT calculations will be applied to this problem in the near future, including but not limited to advanced wavefunction theory-based methods, machine learning (ML)-based potentials and AIMD. Nevertheless, rigorous testing and comprehensive benchmark calculations should be carried out to establish more robust and transferrable computational protocols. Moreover, with the recent development of robust high-throughput DFT/ML workflows for MOFs (Rosen et al., 2019; Rosen et al., 2021; Rosen et al., 2022a; Rosen et al., 2022b) and the establishment of large MOF structure databases (Wilmer et al., 2011; Chung et al., 2014; Colón et al., 2017; Moghadam et al., 2017; Chung et al., 2019; Li et al.,

2021; Rosen et al., 2021; Rosen et al., 2022b), high-throughput computational screening can be adopted to exponentially accelerate the discovery of new MOF catalysts for CO₂ conversion. We believe that computational chemistry study will become an integral part in the massively collaborative effort to solve the omnipresent global climate crisis *via* carbon capture and utilization.

Author contributions

HC contributed to the conceptualization, literature survey, and manuscript writing.

Funding

HC acknowledges the start-up funding from The University of Texas Rio Grande Valley and the Welch Foundation departmental Grant No. #BX-0048.

Conflict of interest

The author declares that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Publisher's note

All claims expressed in this article are solely those of the authors and do not necessarily represent those of their affiliated organizations, or those of the publisher, the editors and the reviewers. Any product that may be evaluated in this article, or claim that may be made by its manufacturer, is not guaranteed or endorsed by the publisher.

References

- An, B., Li, Z., Song, Y., Zhang, J., Zeng, L., Wang, C., et al. (2019). Cooperative copper centres in a metal-organic framework for selective conversion of CO₂ to ethanol. *Nat. Catal.* 2, 709–717. doi:10.1038/s41929-019-0308-5
- Ashley, A. E., and O'Hare, D. (2013). FLP-mediated activations and reductions of CO₂ and CO. *Top. Curr. Chem.* 334, 191–217. doi:10.1007/128_2012_377
- Becke, A. D. (1993). Density-functional thermochemistry. III. The role of exact exchange. *J. Chem. Phys.* 98, 5648–5652. doi:10.1063/1.464913
- Benseghir, Y., Lemarchand, A., Duguet, M., Mialane, P., Gomez-Mingot, M., Roch-Marchal, C., et al. (2020). Co-Immobilization of a Rh catalyst and a kegglin polyoxometalate in the UiO-67 Zr-based metal-organic framework: In depth structural characterization and photocatalytic properties for CO₂ reduction. *J. Am. Chem. Soc.* 142, 9428–9438. doi:10.1021/jacs.0c02425
- Beyzavi, M. H., Klet, R. C., Tussupbayev, S., Borycz, J., Vermeulen, N. A., Cramer, C. J., et al. (2014). A hafnium-based metal-organic framework as an efficient and multifunctional catalyst for facile CO₂ fixation and regioselective and enantioselective epoxide activation. *J. Am. Chem. Soc.* 136, 15861–15864. doi:10.1021/ja508626n
- Beyzavi, M. H., Stephenson, C. J., Liu, Y., Karagiari, O., Hupp, J. T., and Farha, O. K. (2015). Metal-organic framework-based catalysts: Chemical fixation of CO₂ with epoxides leading to cyclic organic carbonates. *Front. Energy Res.* 2, 63. doi:10.3389/fenrg.2014.00063
- Chung, L. W., Sameera, W. M. C., Ramozzi, R., Page, A. J., Hatanaka, M., Petrova, G. P., et al. (2015). The ONIOM method and its applications. *Chem. Rev.* 115, 5678–5796. doi:10.1021/cr5004419
- Chung, Y. G., Camp, J., Haranczyk, M., Sikora, B. J., Bury, W., Krungleviciute, V., et al. (2014). Computation-ready, experimental metal-organic frameworks: A tool to enable high-throughput screening of nanoporous crystals. *Chem. Mat.* 26, 6185–6192. doi:10.1021/cm502594j
- Chung, Y. G., Haldoupis, E., Bucior, B. J., Haranczyk, M., Lee, S., Zhang, H., et al. (2019). Advances, updates, and analytics for the computation-ready, experimental metal-organic framework database: CoRE MOF 2019. *J. Chem. Eng. Data* 64, 5985–5998. doi:10.1021/acs.jced.9b00835

- Colón, Y. J., Gómez-Gualdrón, D. A., and Snurr, R. Q. (2017). Topologically guided, automated construction of metal-organic frameworks and their evaluation for energy-related applications. *Cryst. Growth Des.* 17, 5801–5810. doi:10.1021/acs.cgd.7b00848
- Dhakshinamoorthy, A., Asiri, A. M., and Garcia, H. (2016). Metal-organic framework (MOF) compounds: Photocatalysts for redox reactions and solar fuel production. *Angew. Chem. Int. Ed.* 55, 5414–5445. doi:10.1002/anie.201505581
- Dhankhar, S. S., Das, R., Ugale, B., Pillai, R. S., and Nagaraja, C. M. (2021). Chemical fixation of CO₂ under solvent and Co-Catalyst-free conditions using a highly porous two-fold interpenetrated Cu(II)-Metal-Organic framework. *Cryst. Growth & Des.* 21, 1233–1241. doi:10.1021/acs.cgd.0c01530
- Downes, C. A., and Marinescu, S. C. (2017). Electrocatalytic metal-organic frameworks for energy applications. *ChemSuschem* 10, 4374–4392. doi:10.1002/cssc.201701420
- Elcheikh Mahmoud, M., Audi, H., Assoud, A., Ghaddar, T. H., and Hmadeh, M. (2019). Metal-organic framework photocatalyst incorporating bis(4'-(4-carboxyphenyl)-terpyridine)ruthenium(II) for visible-light-driven carbon dioxide reduction. *J. Am. Chem. Soc.* 141, 7115–7121. doi:10.1021/jacs.9b01920
- Gao, X., Guo, B., Guo, C., Meng, Q., Liang, J., and Liu, J. (2020). Zirconium-based metal-organic framework for efficient photocatalytic reduction of CO₂ to CO: The influence of doped metal ions. *ACS Appl. Mat. Interfaces* 12, 24059–24065. doi:10.1021/acsami.0c05631
- Gutterod, E. S., Lazzarini, A., Fjermestad, T., Kaur, G., Manzoli, M., Bordiga, S., et al. (2020). Hydrogenation of CO₂ to methanol by Pt nanoparticles encapsulated in UiO-67: Deciphering the role of the metal-organic framework. *J. Am. Chem. Soc.* 142, 999–1009. doi:10.1021/jacs.9b10873
- Gutterod, E. S., Pulumati, S. H., Kaur, G., Lazzarini, A., Solemsli, B. G., Gunnaes, A. E., et al. (2020). Influence of defects and H₂O on the hydrogenation of CO₂ to methanol over Pt nanoparticles in UiO-67 metal-organic framework. *J. Am. Chem. Soc.* 142, 17105–17118. doi:10.1021/jacs.0c07153
- Han, B., Ou, X., Deng, Z., Song, Y., Tian, C., Deng, H., et al. (2018). Nickel metal-organic framework monolayers for photoreduction of diluted CO₂: Metal-Node-Dependent activity and selectivity. *Angew. Chem. Int. Ed. Engl.* 57, 17053–17057. doi:10.1002/ange.201811545
- Heshmat, M. (2020). Alternative pathway of CO₂ hydrogenation by lewis-pair-functionalized UiO-66 MOF revealed by metadynamics simulations. *J. Phys. Chem. C* 124, 10951–10960. doi:10.1021/acs.jpcc.0c01088
- Hu, T.-D., Sun, Y.-W., and Ding, Y.-H. (2018). A quantum-chemical insight on chemical fixation carbon dioxide with epoxides co-catalyzed by MIL-101 and tetrabutylammonium bromide. *J. CO₂ Util.* 28, 200–206. doi:10.1016/j.jcou.2018.09.027
- Huang, C. H., and Tan, C. S. (2014). A Review: CO₂ utilization. *Aerosol Air Qual. Res.* 14, 480–499. doi:10.4209/aaqr.2013.10.0326
- Huang, Q., Niu, Q., Ma, N. N., Dong, L. Z., Li, S. L., Li, D. S., et al. (2020). Axial Cl/Br atom-mediated CO₂ electroreduction performance in a stable porphyrin-based metal-organic framework. *Chem. Commun.* 56, 14817–14820. doi:10.1039/d0cc06092e
- Jiang, Z., Xu, X., Ma, Y., Cho, H. S., Ding, D., Wang, C., et al. (2020). Filling metal-organic framework mesopores with TiO₂ for CO₂ photoreduction. *Nature* 586, 549–554. doi:10.1038/s41586-020-2738-2
- Jin, J. (2020). Porphyrin-based metal-organic framework catalysts for photoreduction of CO₂: Understanding the effect of node connectivity and linker metalation on activity. *New J. Chem.* 44, 15362–15368. doi:10.1039/d0nj03507f
- Kang, X., Li, L., Sheveleva, A., Han, X., Li, J., Liu, L., et al. (2020). Electroreduction of carbon dioxide at low over-potential at a metal-organic framework decorated cathode. *Nat. Commun.* 11, 5464. doi:10.1038/s41467-020-19236-4
- Kathalikkattil, A. C., Babu, R., Roshan, R. K., Lee, H., Kim, H., Tharun, J., et al. (2015). An lcy-topology amino acid MOF as eco-friendly catalyst for cyclic carbonate synthesis from CO₂: Structure-DFT corroborated study. *J. Mat. Chem. A Mat.* 3, 22636–22647. doi:10.1039/c5ta05688h
- Kong, X. H., Hu, K. Q., Mei, L., Li, A., Liu, K., Zeng, L. W., et al. (2021). Double-layer nitrogen-rich two-dimensional anionic uranyl-organic framework for cation dye capture and catalytic fixation of carbon dioxide. *Inorg. Chem.* 60, 11485–11495. doi:10.1021/acs.inorgchem.1c01492
- Krishnan, R., Yang, K., Hashem, K., and Jiang, J. (2022). Metallated porphyrinic metal-organic frameworks for CO₂ conversion to HCOOH: A computational screening and mechanistic study. *Mol. Catal.* 527, 112407. doi:10.1016/j.mcat.2022.112407
- Lee, C., Yang, W., and Parr, R. G. (1988). Development of the Colle-Salvetti correlation-energy formula into a functional of the electron density. *Phys. Rev. B* 37, 785–789. doi:10.1103/physrevb.37.785
- Li, A., Perez, R. B., Wiggin, S., Ward, S. C., Wood, P. A., and Fairen-Jimenez, D. (2021). The launch of a freely accessible MOF CIF collection from the CSD. *Matter* 4, 1105–1106. doi:10.1016/j.matt.2021.03.006
- Li, D., Kassymova, M., Cai, X., Zang, S.-Q., and Jiang, H.-L. (2020). Photocatalytic CO₂ reduction over metal-organic framework-based materials. *Coord. Chem. Rev.* 412, 213262. doi:10.1016/j.ccr.2020.213262
- Li, R., Zhang, W., and Zhou, K. (2018). Metal-organic framework-based catalysts for photoreduction of CO₂. *Adv. Mat.* 30, 1705512. doi:10.1002/adma.201705512
- Li, X., Cheetham, A. K., and Jiang, J. (2019). CO₂ cycloaddition with propylene oxide to form propylene carbonate on a copper metal-organic framework: A density functional theory study. *Mol. Catal.* 463, 37–44. doi:10.1016/j.mcat.2018.11.015
- Liao, J., Zeng, W., Zheng, B., Cao, X., Wang, Z., Wang, G., et al. (2020). Highly efficient CO₂ capture and conversion of a microporous acylamide functionalized rht-type metal-organic framework. *Inorg. Chem. Front.* 7, 1939–1948. doi:10.1039/d0qi00231c
- Luo, Z., Wang, J., He, Y., Ao, Q., Deng, Q., Zeng, Z., et al. (2019). A stable Zn-based metal-organic framework as an efficient catalyst for carbon dioxide cycloaddition and alcoholysis at mild conditions. *Catal. Lett.* 150, 1408–1417. doi:10.1007/s10562-019-03053-6
- Ma, R., Qiao, C., Xia, L., Xia, Z., Yang, Q., Xu, Y., et al. (2022). Dynamic metal-iodide bonds in a tetracoordinated cadmium-based metal-organic framework boosting efficient CO₂ cycloaddition under solvent- and cocatalyst-free conditions. *Inorg. Chem.* 61, 7484–7496. doi:10.1021/acs.inorgchem.2c00569
- Maihom, T., Wannakao, S., Boekfa, B., and Limtrakul, J. (2013). Production of formic acid via hydrogenation of CO₂ over a copper-alkoxide-functionalized MOF: A mechanistic study. *J. Phys. Chem. C* 117, 17650–17658. doi:10.1021/jp405178p
- Majidi, L., Ahmadi-paridari, A., Shan, N., Misal, S. N., Kumar, K., Huang, Z., et al. (2021). 2D copper tetrahydroxyquinone conductive metal-organic framework for selective CO₂ electrocatalysis at low overpotentials. *Adv. Mat.* 33, e2004393. doi:10.1002/adma.202004393
- Moghadam, P. Z., Li, A., Wiggin, S. B., Tao, A., Maloney, A. G. P., Wood, P. A., et al. (2017). Development of a cambridge structural database subset: A collection of metal-organic frameworks for past, present, and future. *Chem. Mat.* 29, 2618–2625. doi:10.1021/acs.chemmater.7b00441
- Mori, K., Konishi, A., and Yamashita, H. (2020). Interfacial engineering of PdAg/TiO₂ with a metal-organic framework to promote the hydrogenation of CO₂ to formic acid. *J. Phys. Chem. C* 124, 11499–11505. doi:10.1021/acs.jpcc.0c02457
- Müller, P., Bucior, B., Tuci, G., Luconi, L., Getzschmann, J., Kaskel, S., et al. (2019). Computational screening, synthesis and testing of metal-organic frameworks with a bithiazole linker for carbon dioxide capture and its green conversion into cyclic carbonates. *Mol. Syst. Des. Eng.* 4, 1000–1013. doi:10.1039/c9me00062c
- Olowoyo, J. O., Saini, U., Kumar, M., Valdés, H., Singh, H., Omorogie, M. O., et al. (2020). Reduced graphene oxide/NH₂-MIL-125(Ti) composite: Selective CO₂ photoreduction to methanol under visible light and computational insights into charge separation. *J. CO₂ Util.* 42, 101300. doi:10.1016/j.jcou.2020.101300
- Parmar, B., Patel, P., Pillai, R. S., Tak, R. K., Kureshy, R. I., Khan, N. H., et al. (2019). Cycloaddition of CO₂ with an epoxide-bearing oxindole scaffold by a metal-organic framework-based heterogeneous catalyst under ambient conditions. *Inorg. Chem.* 58, 10084–10096. doi:10.1021/acs.inorgchem.9b01234
- Perdew, J. P., Burke, K., and Ernzerhof, M. (1996). Generalized gradient approximation made simple. *Phys. Rev. Lett.* 77, 3865–3868. doi:10.1103/physrevlett.77.3865
- Qi, S.-C., Yang, Z.-H., Zhu, R.-R., Lu, X.-J., Xue, D.-M., Liu, X.-Q., et al. (2021). The cascade catalysis of the porphyrinic zirconium metal-organic framework PCN-224-Cu for CO₂ conversion to alcohols. *J. Mat. Chem. A Mat.* 9, 24510–24516. doi:10.1039/d1ta06950k
- Rachuri, Y., Kurisingal, J. F., Chitumalla, R. K., Vuppala, S., Gu, Y., Jang, J., et al. (2019). Adenine-based Zn(II)/Cd(II) metal-organic frameworks as efficient heterogeneous catalysts for facile CO₂ fixation into cyclic carbonates: A DFT-supported study of the reaction mechanism. *Inorg. Chem.* 58, 11389–11403. doi:10.1021/acs.inorgchem.9b00814
- Rosen, A. S., Fung, V., Huck, P., O'Donnell, C. T., Horton, M. K., Truhlar, D. G., et al. (2022). High-throughput predictions of metal-organic framework electronic properties: Theoretical challenges, graph neural networks, and data exploration. *npj Comput. Mat.* 8, 112. doi:10.1038/s41524-022-00796-6
- Rosen, A. S., Iyer, S. M., Ray, D., Yao, Z., Aspuru-Guzik, A., Gagliardi, L., et al. (2021). Machine learning the quantum-chemical properties of metal-organic frameworks for accelerated materials discovery. *Matter* 4, 1578–1597. doi:10.1016/j.matt.2021.02.015

- Rosen, A. S., Notestein, J. M., and Snurr, R. Q. (2019). Identifying promising metal-organic frameworks for heterogeneous catalysis via high-throughput periodic density functional theory. *J. Comput. Chem.* 40, 1305–1318. doi:10.1002/jcc.25787
- Rosen, A. S., Notestein, J. M., and Snurr, R. Q. (2022). Realizing the data-driven, computational discovery of metal-organic framework catalysts. *Curr. Opin. Chem. Eng.* 35, 100760. doi:10.1016/j.coche.2021.100760
- Schaffner, B., Schaffner, F., Verevkin, S. P., and Borner, A. (2010). Organic carbonates as solvents in synthesis and catalysis. *Chem. Rev.* 110, 4554–4581. doi:10.1021/cr900393d
- Sharma, N., Dhankhar, S. S., Kumar, S., Kumar, T. J. D., and Nagaraja, C. M. (2018). Rational design of a 3D Mn(II)-Metal-Organic framework based on a nonmetallated porphyrin linker for selective capture of CO₂ and one-pot synthesis of styrene carbonates. *Chem. Eur. J.* 24, 16662–16669. doi:10.1002/chem.201803842
- Song, J. L., Zhang, Z. F., Hu, S. Q., Wu, T. B., Jiang, T., and Han, B. X. (2009). MOF-5/n-Bu₄NBr: An efficient catalyst system for the synthesis of cyclic carbonates from epoxides and CO₂ under mild conditions. *Green Chem.* 11, 1031–1036. doi:10.1039/b902550b
- Stanley, P. M., Thomas, C., Thyrhaug, E., Urstoeger, A., Schuster, M., Hauer, J., et al. (2021). Entrapped molecular photocatalyst and photosensitizer in metal-organic framework nanoreactors for enhanced solar CO₂ reduction. *ACS Catal.* 11, 871–882. doi:10.1021/acscatal.0c04673
- Stephan, D. W., and Erker, G. (2010). Frustrated Lewis pairs: Metal-free hydrogen activation and more. *Angew. Chem. Int. Ed.* 49, 46–76. doi:10.1002/anie.200903708
- Sun, D., Liu, W., Qiu, M., Zhang, Y., and Li, Z. (2015). Introduction of a mediator for enhancing photocatalytic performance via post-synthetic metal exchange in metal-organic frameworks (MOFs). *Chem. Commun.* 51, 2056–2059. doi:10.1039/c4cc09407g
- Vosko, S. H., Wilk, L., and Nusair, M. (1980). Accurate spin-dependent electron liquid correlation energies for local spin-density calculations - a critical analysis. *Can. J. Phys.* 58, 1200–1211. doi:10.1139/p80-159
- Wang, C., Liu, X.-M., Zhang, M., Geng, Y., Zhao, L., Li, Y.-G., et al. (2019). Two-dimensional cobaltporphyrin-based cobalt-organic framework as an efficient photocatalyst for CO₂ reduction reaction: A computational study. *ACS Sustain. Chem. Eng.* 7, 14102–14110. doi:10.1021/acssuschemeng.9b02699
- Wang, W. M., Wang, W. T., Wang, M. Y., Gu, A. L., Hu, T. D., Zhang, Y. X., et al. (2021). A porous copper-organic framework assembled by [Cu₁₂] nanocages: Highly efficient CO₂ capture and chemical fixation and theoretical DFT calculations. *Inorg. Chem.* 60, 9122–9131. doi:10.1021/acs.inorgchem.1c01104
- Wang, X.-K., Liu, J., Zhang, L., Dong, L.-Z., Li, S.-L., Kan, Y.-H., et al. (2019). Monometallic catalytic models hosted in stable metal-organic frameworks for tunable CO₂ photoreduction. *ACS Catal.* 9, 1726–1732. doi:10.1021/acscatal.8b04887
- Wang, Y., Huang, N. Y., Shen, J. Q., Liao, P. Q., Chen, X. M., and Zhang, J. P. (2018). Hydroxide ligands cooperate with catalytic centers in metal-organic frameworks for efficient photocatalytic CO₂ reduction. *J. Am. Chem. Soc.* 140, 38–41. doi:10.1021/jacs.7b10107
- Wang, Y. R., Huang, Q., He, C. T., Chen, Y., Liu, J., Shen, F. C., et al. (2018). Oriented electron transmission in polyoxometalate-metalloporphyrin organic framework for highly selective electroreduction of CO₂. *Nat. Commun.* 9, 4466. doi:10.1038/s41467-018-06938-z
- Wilmer, C. E., Leaf, M., Lee, C. Y., Farha, O. K., Hauser, B. G., Hupp, J. T., et al. (2011). Large-scale screening of hypothetical metal-organic frameworks. *Nat. Chem.* 4, 83–89. doi:10.1038/nchem.1192
- Wu, Y., Song, X., Xu, S., Yu, T., Zhang, J., Qi, Q., et al. (2019). [(CH₃)₂NH₂][M(COOH)₃] (M=Mn, Co, Ni, Zn) MOFs as highly efficient catalysts for chemical fixation of CO₂ and DFT studies. *Mol. Catal.* 475, 110485. doi:10.1016/j.mcat.2019.110485
- Wu, Y., Song, X., Zhang, J., Xu, S., Gao, L., Zhang, J., et al. (2019). Mn-based MOFs as efficient catalysts for catalytic conversion of carbon dioxide into cyclic carbonates and DFT studies. *Chem. Eng. Sci.* 201, 288–297. doi:10.1016/j.ces.2019.02.032
- Xu, G., Zhang, H., Wei, J., Zhang, H. X., Wu, X., Li, Y., et al. (2018). Integrating the g-C₃N₄ nanosheet with B-H bonding decorated metal-organic framework for CO₂ activation and photoreduction. *ACS Nano* 12, 5333–5340. doi:10.1021/acsnano.8b00110
- Xu, K., Moeljadi, A. M. P., Mai, B. K., and Hirao, H. (2018). How does CO₂ react with styrene oxide in Co-MOF-74 and Mg-MOF-74? Catalytic mechanisms proposed by QM/MM calculations. *J. Phys. Chem. C* 122, 503–514. doi:10.1021/acs.jpcc.7b09790
- Yan, Z. H., Du, M. H., Liu, J., Jin, S., Wang, C., Zhuang, G. L., et al. (2018). Photo-generated dinuclear {Eu(II)}₂ active sites for selective CO₂ reduction in a photosensitizing metal-organic framework. *Nat. Commun.* 9, 3353. doi:10.1038/s41467-018-05659-7
- Yang, K., and Jiang, J. (2020). Computational design of a metal-based frustrated Lewis pair on defective UiO-66 for CO₂ hydrogenation to methanol. *J. Mat. Chem. A Mat.* 8, 22802–22815. doi:10.1039/d0ta07051c
- Yang, K., and Jiang, J. (2022). Highly efficient CO₂ conversion on a robust metal-organic framework Cu(I)-MFU-4l: Prediction and mechanistic understanding from DFT calculations. *J. CO₂ Util.* 63, 102148. doi:10.1016/j.jcou.2022.102148
- Yang, K., and Jiang, J. (2021). Transforming CO₂ into methanol with N-heterocyclic carbene-stabilized coinage metal hydrides immobilized in a metal-organic framework UiO-68. *ACS Appl. Mat. Interfaces* 13, 58723–58736. doi:10.1021/acscami.1c18885
- Ye, J., and Johnson, J. K. (2016). Catalytic hydrogenation of CO₂ to methanol in a Lewis pair functionalized MOF. *Catal. Sci. Technol.* 6, 8392–8405. doi:10.1039/c6cy01245k
- Ye, J., and Johnson, J. K. (2015). Design of Lewis pair-functionalized metal organic frameworks for CO₂ hydrogenation. *ACS Catal.* 5, 2921–2928. doi:10.1021/acscatal.5b00396
- Ye, J., and Johnson, J. K. (2015). Screening Lewis pair moieties for catalytic hydrogenation of CO₂ in functionalized UiO-66. *ACS Catal.* 5, 6219–6229. doi:10.1021/acscatal.5b01191
- Ye, J., Li, L., and Johnson, J. K. (2018). The effect of topology in Lewis pair functionalized metal organic frameworks on CO₂ adsorption and hydrogenation. *Catal. Sci. Technol.* 8, 4609–4617. doi:10.1039/c8cy01018h
- Yu, C. H., Huang, C. H., and Tan, C. S. (2012). A Review of CO₂ capture by absorption and adsorption. *Aerosol Air Qual. Res.* 12, 745–769. doi:10.4209/aaqr.2012.05.0132
- Yu, F., Jing, X., Wang, Y., Sun, M., and Duan, C. (2021). Hierarchically porous metal-organic framework/MoS₂ interface for selective photocatalytic conversion of CO₂ with H₂O into CH₃COOH. *Angew. Chem. Int. Ed. Engl.* 60, 25053–25057. doi:10.1002/ange.202108892
- Zhang, G., Wei, G., Liu, Z., Oliver, S. R. J., and Fei, H. (2016). A robust sulfonate-based metal-organic framework with permanent porosity for efficient CO₂ capture and conversion. *Chem. Mat.* 28, 6276–6281. doi:10.1021/acs.chemmater.6b02511
- Zhang, J., An, B., Li, Z., Cao, Y., Dai, Y., Wang, W., et al. (2021). Neighboring Zn-Zr sites in a metal-organic framework for CO₂ hydrogenation. *J. Am. Chem. Soc.* 143, 8829–8837. doi:10.1021/jacs.1c03283
- Zhao, Y., and Truhlar, D. G. (2006). A new local density functional for main-group thermochemistry, transition metal bonding, thermochemical kinetics, and noncovalent interactions. *J. Chem. Phys.* 125, 194101. doi:10.1063/1.2370993
- Zhao, Y., and Truhlar, D. G. (2008). The M06 suite of density functionals for main group thermochemistry, thermochemical kinetics, noncovalent interactions, excited states, and transition elements: Two new functionals and systematic testing of four M06-class functionals and 12 other functionals. *Theor. Chem. Acc.* 120, 215–241. doi:10.1007/s00214-007-0310-x
- Zhao, Y., Zheng, L., Jiang, D., Xia, W., Xu, X., Yamauchi, Y., et al. (2021). Nanoengineering metal-organic framework-based materials for use in electrochemical CO₂ reduction reactions. *Small* 17, 2006590. doi:10.1002/smll.202006590
- Zhao, Z. H., Zheng, K., Huang, N. Y., Zhu, H. L., Huang, J. R., Liao, P. Q., et al. (2021). A Cu(II)/metal-organic framework as a tandem catalyst for highly selective CO₂ electroreduction to C₂H₄. *Chem. Commun.* 57, 12764–12767. doi:10.1039/d1cc05376k
- Zhong, H., Ghorbani-Asl, M., Ly, K. H., Zhang, J., Ge, J., Wang, M., et al. (2020). Publisher Correction: Synergistic electroreduction of carbon dioxide to carbon monoxide on bimetallic layered conjugated metal-organic frameworks. *Nat. Commun.* 11, 1721. doi:10.1038/s41467-020-15668-0
- Zhu, H.-L., Huang, J.-R., Zhang, X.-W., Wang, C., Huang, N.-Y., Liao, P.-Q., et al. (2021). Highly efficient electroconversion of CO₂ into CH₄ by a metal-organic framework with trigonal pyramidal Cu(I)N₃ active sites. *ACS Catal.* 11, 11786–11792. doi:10.1021/acscatal.1c02980
- Zhu, Y., Zheng, J., Ye, J., Cui, Y., Koh, K., Kovarik, L., et al. (2020). Copper-zirconia interfaces in UiO-66 enable selective catalytic hydrogenation of CO₂ to methanol. *Nat. Commun.* 11, 5849. doi:10.1038/s41467-020-19438-w